

AD-A103 369

ARMY ENGINEER WATERWAYS EXPERIMENT STATION VICKSBURG--ETC F/G 11/2
CHARACTERIZATION AND REACTIVITY OF SILICA FUME.(U)

JUL 81 A D BUCK, J P BURKES

WES/MP/SL-81-13

CTIAC-47

NL

UNCLASSIFIED

1 OF 1
AD A
105560


END

DATE

FORMED

10-81

DTIC



LEVEL *IX*



MISCELLANEOUS PAPER SL-81-13

CHARACTERIZATION AND REACTIVITY OF SILICA FUME

by

Alan D. Buck, J. P. Burkes

Structures Laboratory
U. S. Army Engineer Waterways Experiment Station
P. O. Box 631, Vicksburg, Miss. 39180

July 1981

Final Report

Approved For Public Release; Distribution Unlimited

DTIC
ELECTE
AUG 26 1981
S D H



Prepared for Office, Chief of Engineers, U. S. Army
Washington, D. C. 20314

Under Civil Works Investigation Work Units
31294, 31295, and 31345

DTIC FILE COPY

81 8 26 015

AD A103369

Destroy this report when no longer needed. Do not return
it to the originator.

The findings in this report are not to be construed as an official
Department of the Army position unless so designated
by other authorized documents.

The contents of this report are not to be used for
advertising, publication, or promotional purposes.
Citation of trade names does not constitute an
official endorsement or approval of the use of
such commercial products.

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Miscellaneous Paper SL-81-13	2. GOVT ACCESSION NO. AD-A103 369	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) CHARACTERIZATION AND REACTIVITY OF SILICA FUME,		5. TYPE OF REPORT & PERIOD COVERED Final report
7. AUTHOR(s) Alan D. Buck J. P. Burkes		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS U. S. Army Engineer Waterways Experiment Station Structures Laboratory P. O. Box 631, Vicksburg, Miss. 39180		8. CONTRACT OR GRANT NUMBER(s) WES/INP/21-71-12
11. CONTROLLING OFFICE NAME AND ADDRESS Office, Chief of Engineers, U. S. Army Washington, D. C. 20314		10. FUNDING ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS CWI Work Units 31294, 31295, and 31345
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE July 1981
		13. NUMBER OF PAGES 10
		15. SECURITY CLASS. (of this report) Unclassified
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES This is CTIAC Report No. 47. Report is available from National Technical Information Service, 5285 Port Royal Road, Springfield, Va. 22151.		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Concrete technology Laboratory tests Pozzolans Silica fume		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Silica fume is a fine, siliceous powder that is a by-product of producing silicon metal or ferrosilicon in a reducing environment in an electric furnace. Recent research work on cementitious materials included characterization of such a silica fume from Alabama by chemical, physical, and petrographic tests. In addition, properties of mixtures of this fume with water and calcium hydroxide were studied. Compressive strengths were determined at different (Continued)		

DTIC
COLLECTED
JUL 13 1981

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

411 115

mit

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

20. ABSTRACT (Continued).

ages, and the composition and microstructure of the hydrated material was studied by X-ray diffraction and by scanning electron microscopy.

The results show that the silica fume is characterized by small spheres of high silica content, by very high surface area, and is almost totally amorphous. Physical tests showed that it is a pozzolan, is effective in reducing expansion due to alkali-silica reaction, and increases the sulfate resistance of mortars. Combination of this material with water and calcium hydroxide results in the formation of extremely well crystallized Type I calcium silicate hydrate (CSH-I).

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

PREFACE

The research that produced the results given in this paper was conducted for the Office, Chief of Engineers. It was part of Civil Works Investigation Work Unit 31294, "Minimize Alkali-Silica Reaction," Work Unit 31295, "Substitutes for Sulfate Resistant Cement," and Work Unit 31345, "Variations in Cementitious Media." The research was done in the Concrete Technology Division (CTD) of the Structures Laboratory (SL), U. S. Army Engineer Waterways Experiment Station (WES). Original approval for all of these investigations was provided in a Disposition Form dated 19 May 1975, Comment 1, Subject, "FY 76 and 76T Civil Works Research and Development Program," from Chief, Research and Development Office, DAEN-RDZ-A, to the Commander/Director of WES.

The work was done under the direction of Messrs. B. Mather, Chief, SL, and John M. Scanlon, Chief, CTD. Mrs. Katharine Mather was Project Leader for each of the projects. Mr. Alan D. Buck prepared this report from data provided by Mr. J. P. Burkes.

Funds for the publication of this report were provided from those made available for operation of the Concrete Technology Information Analysis Center (CTIAC). This is CTIAC Report No. 47.

LTC David C. Girardot, Jr., CE, was Acting Commander and Mr. F. R. Brown was Acting Director of WES when this report was prepared.

Accession For	
NTIS GRA&I	<input checked="checked" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution /	
Availability Codes	
Dist Special	
A	

CHARACTERIZATION AND REACTIVITY OF SILICA FUME*

INTRODUCTION

Silica fume, also known as silica flour, amorphous silica, or volatilized silica, is a by-product waste material from the production of silicon or ferrosilicon metal.

Sixteen such fumes were examined at the Structures Laboratory of the U. S. Army Engineer Waterways Experiment Station (WES) as part of a Civil Works Investigation (CWI), Work Unit "Variations in Cementitious Media." One of these, from Alabama, was studied more extensively as part of two other CWI Work Units. These were "Substitutes for Sulfate-Resistant Cements" and "Minimize Alkali-Silica Reaction."

Silica fume is a fine powder that is composed of tiny spheres of amorphous silica and fits the definition of a pozzolan in that it hardens when combined with calcium hydroxide (CH) and water (1). Considerable work in other countries has already called attention to this material as a solid waste problem and as a potentially useful material in cement and concrete (2-4).

MATERIALS AND METHODS

The silica fume was identified as AD-536(2). The CH was a commercial product. Distilled water was used.

Preliminary work included characterization of the fume by chemical analysis, physical tests, X-ray diffraction (XRD), and scanning electron microscopy (SEM).

The original mixtures were made using two parts of fume to one part CH by mass and enough water to achieve normal consistency by ASTM C 187. Other mixtures were made with both two parts and one part of fume to one part of CH and more water.

Other mixtures at both fume to CH ratios were made to have a flow between 95 to 105. One mixture was made to the same flow but with one part of fume to 2.25 parts of CH. Cubes were molded from all mixtures, stored for 24 h at 23°C and thereafter at 38°C until being broken or examined by XRD and SEM. The initial series of tests were made at 7-, 28-, and 90-day ages. Some of the later mixtures were also tested at 56-, 180-, and 365-day ages.

Tests to evaluate the effectiveness of this fume in controlling

* Prepared for presentation at Third International Conference on Cement Microscopy in Houston, Texas, 16-19 March 1981.

or reducing alkali-silica reaction and sulfate attack were made. The details will be reported elsewhere.

RESULTS

Tests of the fume (AD-536(2)) showed it to contain about 96 percent SiO_2 , a little over 1 percent Al_2O_3 , and much smaller amounts of iron, magnesium, calcium, sulfur, sodium, and moisture. It was completely amorphous by XRD. SEM showed it to consist of small spheres.

The fineness of the fume was determined by the air-permeability method (ASTM Designation: C 204). However the material could not be used in the prescribed manner to produce a bed having a porosity of 0.530 ± 0.005 . Hence the surface area was measured at three porosities, and by extrapolation to a porosity of 0.530 the surface area was judged to be $13 \text{ m}^2/\text{g}$. Silica fume from Norway and Sweden has been reported as having a surface area of about $20 \text{ m}^2/\text{g}$ (4). These fumes may be finer than the Alabama fume or the difference may lie in the extrapolation used. In any case, the Alabama fume was very much finer than most portland cements. Experience has indicated that handling of such fine powders may be the main problem standing in the way of their use as a pozzolan (4).

Data on four paste mixtures including water to solids ratios (W/S) from 0.69 to 1.06 and fume to CH ratios of 2 to 1, 1 to 1, and 1 to 2.25 are shown in Table 1. These strengths ranged from 5.4 MPa (770 psi) to 33.4 MPa (4770 psi). In general, the strengths were about 20 to 33 MPa when W/S was about 0.7, about 10 MPa when W/S was about 1.0 with one or two parts of fume, and about 7 MPa when W/S was about 1.0 and the fume content was sharply reduced. There was no detectable effect on strength of the amount of fume when it was 1 or 2 parts of fume to 1 part CH and W/S was about 1.0.

XRD showed that the amorphous fume had combined with the CH and water to form unusually well crystallized calcium silicate hydrate-I (CSH-I) by 7 days and the XRD patterns always showed this at all ages. Part of a typical XRD pattern is shown in Figure 1. CSH, unspecified as to Type I or II, is usually only detectable in XRD patterns of hydrated portland cement paste if at all as a vague hump. The partial XRD pattern shown in Figure 1 shows most of the peaks listed by Taylor (5) as CSH-I. Hara and Inoue (6) report the formation of jennite from fumed silica but their work was carried out at 80°C while our work took place at 38°C . Jennite is more crystalline than CSH. Study of XRD patterns of the different mixtures showed the following:

a. XRD peaks for CH were no longer found in samples of any of the mixtures containing two parts of fume after 7 days storage. Such peaks

were present at 7 days in one of the mixtures containing one part of fume but were gone by 28 days.

b. A mixture containing one part of fume showed the best development of a 1.3-nm (13 Å) peak by XRD. In most XRD patterns there was only a slight indication of a spacing in that area.

c. CSH-I was the type of CSH found in all of the XRD patterns. The mixture containing 1.7 parts CaO to SiO₂ (Table 1) was made to encourage the formation of CSH-II since this compound requires more CaO than CSH-I (5), but no CSH-II formed. This mixture contained excess CH as it was present in large amounts in XRD patterns to one year.

d. There did not seem to be any significant change in the amount or crystallinity of the CSH-I with time or mixture proportions. It was always present with the XRD patterns by the 7-day testing age.

Scanning electron micrographs of all mixtures at all test ages showed generally consistent features regardless of mixture proportions or age. While most of the fume seemed to have been used up in the chemical reaction, an occasional residual sphere of the fume was seen at an age of one year. Figures 2, 3, and 4 show typical microstructures at different magnifications of a 7-day-old mixture made with one part fume, one part CH, and W/S of about 1.2. Since the starting materials were generally all used up in the hydration of the fume and XRD patterns showed only CSH-I, it was assumed that the material seen in these micrographs, if not obviously residual fume or CH, was CSH-I. Figure 4 is a particularly good example of this CSH-I morphology. This structure seems to be crumpled foils as mentioned by Taylor (5, Plate 27 and pg. 372) for CSH-I. It also resembles the reticulated network described and illustrated by Diamond (7,8) for CSH in cement paste.

K. Mather (9, 10) has reported on work at WES showing that this fume (AD-536(2)) is very effective in reducing expansion due to sulfate attack. Other work at WES has shown it is equally as effective in reducing expansion due to alkali-silica reaction.

CONCLUSIONS

This silica fume was composed of small amorphous spheres and had an SiO₂ content of about 96 percent.

It was an effective pozzolan which shows promise for controlling or reducing alkali-silica reaction and sulfate attack in concrete.

Combination of this fume in different amounts with CH and water led to the formation of CSH-I by 7 days.

This CSH-I was much more crystalline than the CSH found in cement paste hydrated at normal temperatures.

REFERENCES

1. American Society for Testing and Materials, "Standard Specification for Fly Ash and Raw or Calcined Natural Pozzolan for Use as a Mineral Admixture in Portland Cement Concrete" (ASTM Designation: C 618-80), Part 14, 1980 Annual Book of ASTM Standards, Philadelphia.
2. Asgeirsson, H., and Gudmundsson, G., "Pozzolanic Activity of Silica Dust," Cement and Concrete Research, Vol. 9, pp. 249-252, 1979, New York.
3. Traetteberg, A., "Silica Fumes as a Pozzolanic Material," Il Cemento, Vol. 75, No. 3, pp. 369-375, 1978, Rome.
4. Gutt, W., and Nixon, P. J., "Use of Waste Materials in the Construction Industry," Materials and Structures, Vol. 12, No. 70, pp. 289-290, 1979, Paris.
5. Taylor, H. F. W., The Chemistry of Cements, Vol. 2, pg. 327, 1964, Academic Press, N.Y.
6. Hara, N., and Inoue, N., "Formation of Jennite from Fumed Silica," Cement and Concrete Research, Vol. 10, pp. 677-682, 1980, N.Y.
7. Diamond, S., "Application of SEM to the Study of Hydrated Cement," in Proc. of 3rd Annual SEM Symposium, pp. 385-392, 28-30 April, 1970, Illinois Institute of Technology, Chicago.
8. Diamond, S., "Structure of Cement Paste," in Hydraulic Cement Pastes: Their Structure and Properties, Proc. of a Conference held at the University of Sheffield, 8-9 April 1976, pp. 2-30, Cement and Concrete Assoc., Wexham Springs, Great Britain.
9. Mather, K., "Current Research in Sulfate Resistance at the Waterways Experiment Station," presented at the Verbeck Memorial Symposium, sponsored by ACI Committee 201 on Durability, 5 March 1980, Las Vegas, Nev., in press.
10. Mather, K., "Factors Affecting Sulfate Resistance of Mortars," U. S. Army Engineer Waterways Experiment Station, Miscellaneous Paper SL-80-17, October 1980, Vicksburg, Miss., also in press for Proc. 7th International Cong. on Chem. of Cement, Paris.

TABLE 1
Physical Data for Pastes Made Using Silica Fume and Calcium Hydroxide

Line to Silica Ratio	Proportions of Fume to Calcium Hydroxide	Flow	Water to Solids Ratio	Compressive Strength at Ages (Days) Shown Below, MPa*				
				7	28	56	90	365
~0.4	2:1	--	0.69	20.1	31.1	--	33.4	--
~0.4	2:1	93	1.06	8.8	11.5	11.6	11.3	11.3
~0.8	1:1	95	0.98	9.3	11.8	10.8	11.6	10.9
~1.7	1:2.25	101	0.93	5.5	7.1	7.6	6.9	7.1
							5.4	

* psi x 0.006894757 = MPa



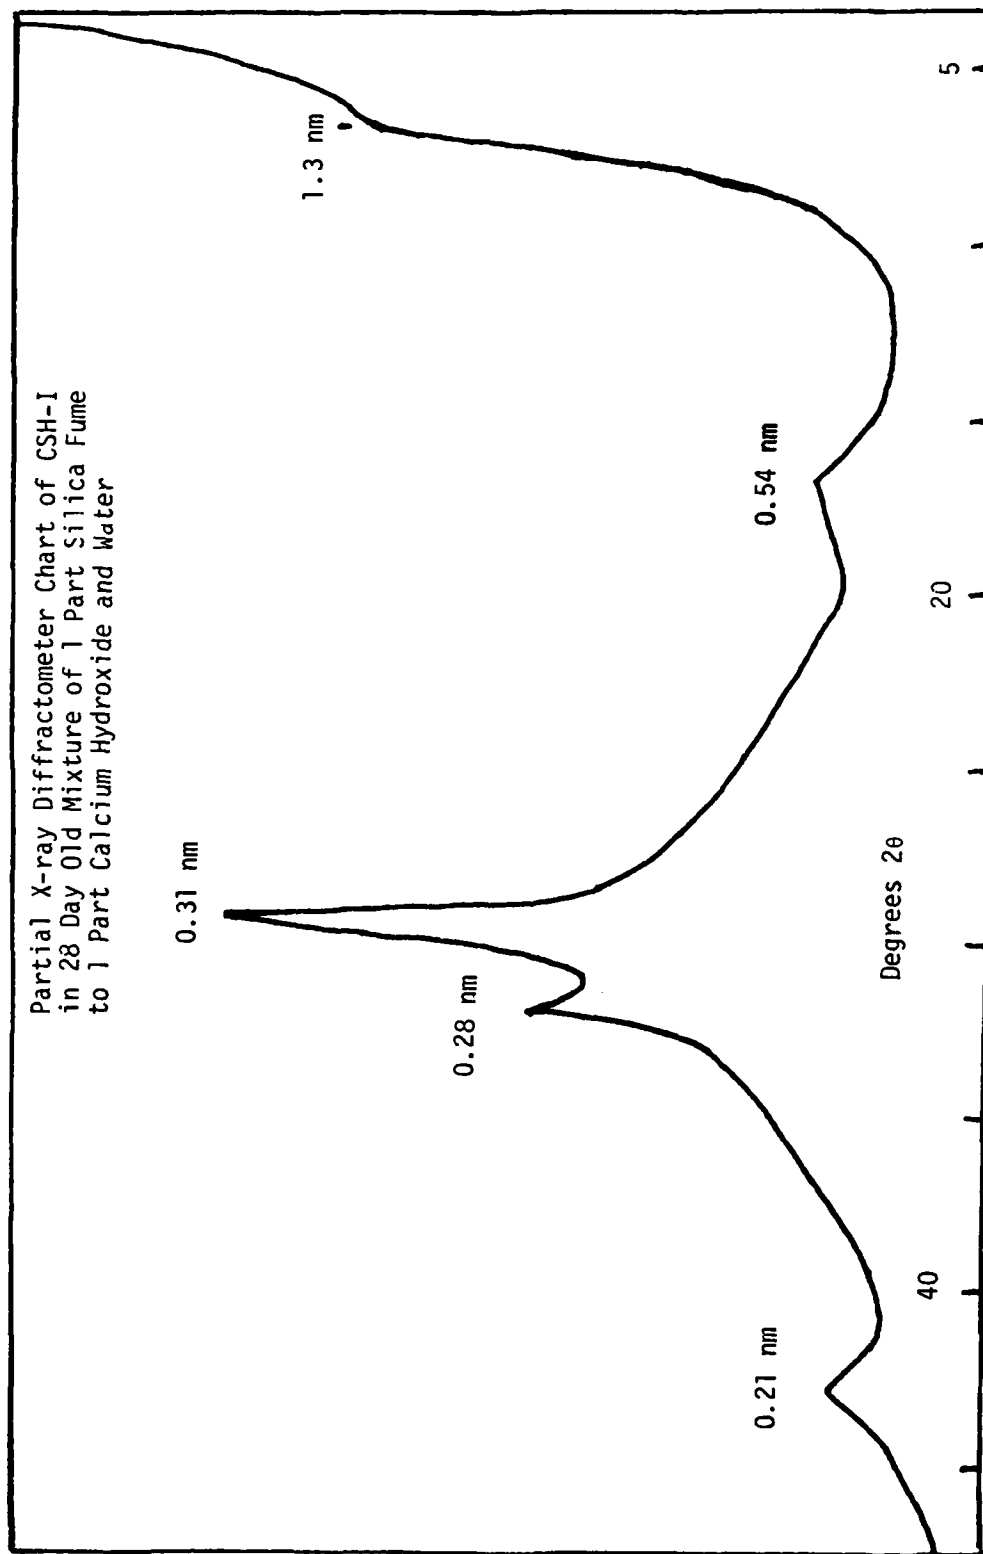


Figure 1

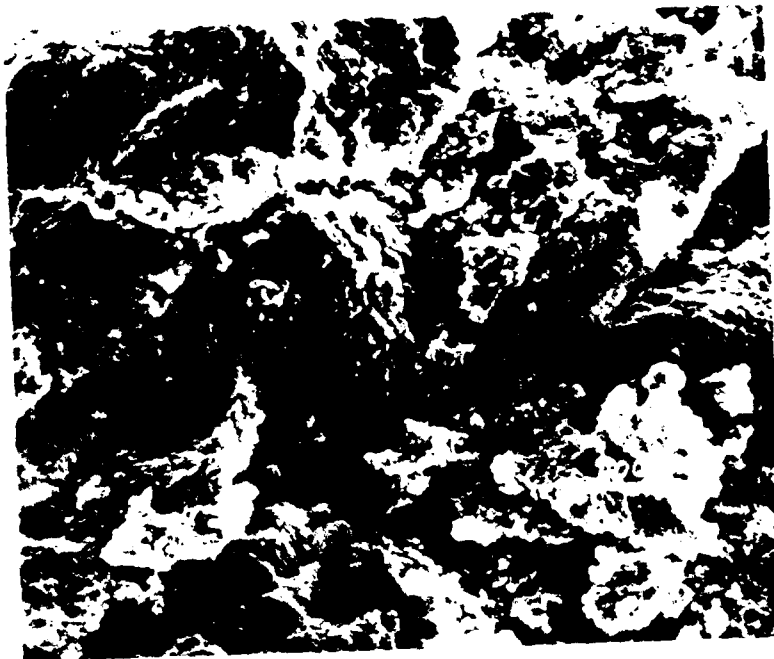

SEM micrograph showing broken surface of 7-day old mixture made with 1 part fume, 1 part CIL, and water to solids ratio about 1.2. Typical appearance at low magnification.

Figure 2

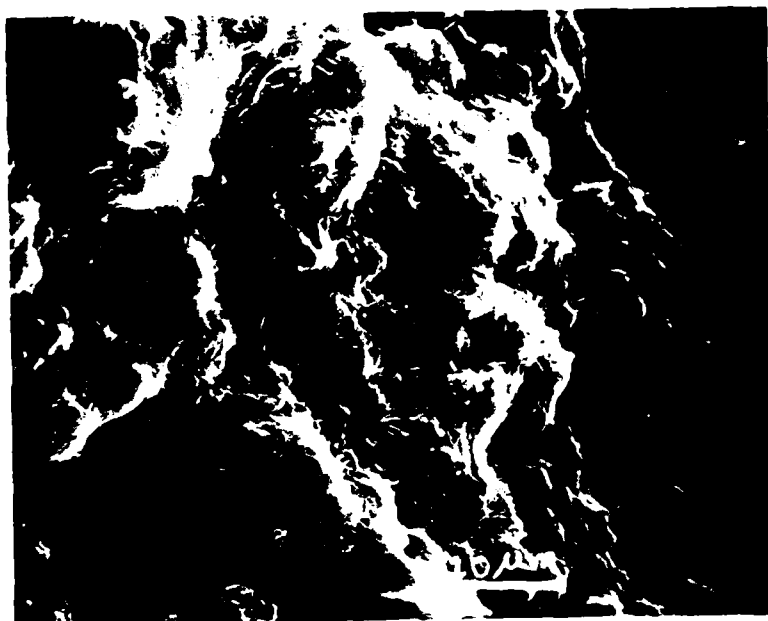

Enlargement of central portion of Figure 2. Void space and details of the CSH-I are becoming evident.

Figure 3



Enlargement of central portion of Figure 3. The size and shape of the CSH-I crystals are apparent.

Figure 4

In accordance with letter from DAEN-RDC, DAEN-ASI dated 22 July 1977, Subject: Facsimile Catalog Cards for Laboratory Technical Publications, a facsimile catalog card in Library of Congress MARC format is reproduced below.

Buck, Alan D.

Characterization and reactivity of silica fume : final report / by Alan D. Buck, J. P. Burkes (Structures Laboratory, U.S. Army Engineer Waterways Experiment Station). -- Vicksburg, Miss. : The Station ; Springfield, Va. : available from NTIS, [1981].

5, [5] p. : ill. ; 27 cm. -- (Miscellaneous paper / U.S. Army Engineer Waterways Experiment Station ; SL-81-13)

Cover title.

"July 1981."

"Prepared for Office, Chief of Engineers, U.S. Army under Civil Works Investigation Work Units 31294, 31295, and 31345."

Bibliography: p. 5.

1. Concrete construction. 2. Concrete--Testing.
3. Pozzuolanas. 4. Silica. I. Burkes, J.P.

Buck, Alan D.

Characterization and reactivity of silica : ... 1981.
(Card 2)

II. United States. Army. Corps of Engineers. Office of the Chief of Engineers. III. U.S. Army Engineer Waterways Experiment Station. Structures Laboratory. IV. Title V. Series: Miscellaneous paper (U.S. Army Engineer Waterways Experiment Station) ; SL-81-13.
TA7.W34m no.SL-81-13

DATE
ILMED
-8